


Material: BMFP-1220

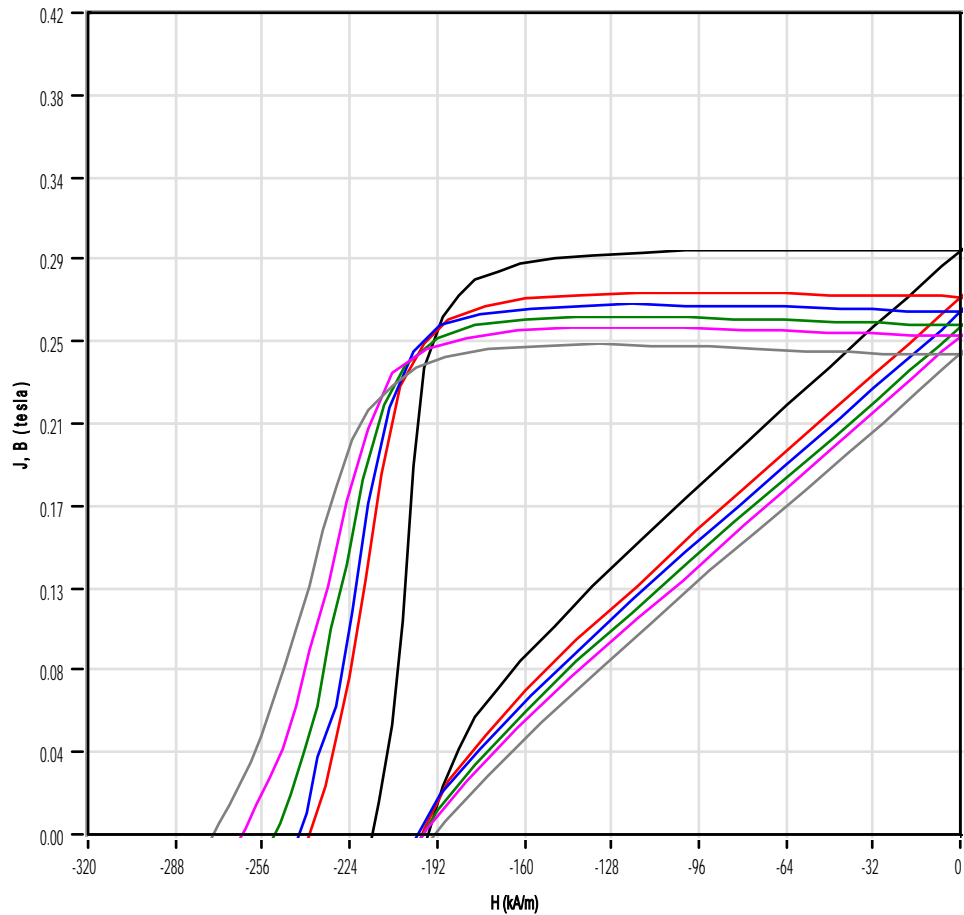

File	Sample	Material	Section shape	T (°C)	Br (T)	HcB (kA/m)	HcJ (kA/m)	BHmax (kJ/m³)	BA (T)	HA (kA/m)	Hknee (kA/m)
Sample 20°	603021	Bonded ferrite	Circle	20.0	0.298	194.88	215.44	17.60	0.153	115.37	187.99
Sample 80°	603021	Bonded ferrite	Circle	80.0	0.275	197.72	238.88	15.21	0.138	110.01	198.26
Sample 100°	603021	Bonded ferrite	Circle	100.0	0.267	198.52	242.68	14.57	0.134	108.42	202.36
Sample 120°	603021	Bonded ferrite	Circle	120.0	0.260	197.02	251.62	13.94	0.131	106.69	206.00
Sample 130°	603021	Bonded ferrite	Circle	130.0	0.255	196.63	262.96	13.30	0.127	104.63	210.30
Sample 150°	603021	Bonded ferrite	Circle	150.0	0.246	192.75	273.88	12.41	0.123	100.59	214.10